EVALUATION REPORT OF UNION CORRUGATING COMPANY '26 GA. PBR PANEL'

FLORIDA BUILDING CODE 6TH EDITION (2017) FLORIDA PRODUCT APPROVAL FL 9555.6-R4 STRUCTURAL COMPONENTS ROOF DECK

Prepared For: Union Corrugating Company 701 S. King St. Fayetteville, NC 28301 Telephone: (910) 483-0479 Fax: (910) 483-1091

Prepared By: Bala Sockalingam, Ph.D., P.E. Florida Professional Engineer #62240 1216 N Lansing Ave., Suite C Tulsa, OK 74106 Telephone: (918) 492-5992 FAX: (866) 366-1543

This report consists of Evaluation Report (3 Pages including cover) Installation Details (1 Page) Load Span Table (1 Page)

> Report No. C2172-6 Date: 8.20.2017




Manufacturer:	Union Corrugating Company	
Product Name:	PBR Panel	
Panel Description:	36" wide coverage with (4) 1-1/4" high ribs	
Materials:	Min. 26 ga., 80 ksi steel or min. 24 ga., 50 ksi steel. Galvanized coated steel (ASTM A653) or Galvalume coated steel (ASTM A792) or painted steel (ASTM A755).	
Support Description:	Min. 16 ga., 50 ksi steel section. (Must be designed by others)	
Slope:	1/2:12 or greater in accordance with FBC 2017 Section 1507.4.2	
Design Pressure: (Factor of Safety = 2) (3 or more spans)	 -45.5 psf @ support spacing of 60 o.c. -163.0 psf @ support spacing of 20 o.c. 32 psf @ support spacing of 60 o.c. 96 psf @ support spacing of 20 o.c. 	
Panel Attachment: At panel ends	#12-14 x 1-1/4" long SDS with washer @ 7"-5"-7" o.c. across panel width	
At interior supports	#12-14 x 1-1/4" long SDS with washer @ 12" o.c. across panel width	
Sidelap Attachment:	$\frac{1}{4}$ "-14 x 7/8" long SDS with washer @ 24" o.c.	
Test Standards:	Roof assembly tested in accordance with ASTM E1592-05 (2012) 'Test Method for Structural Performance of Sheet Metal Roof and Siding Systems by Uniform Static Air Pressure Difference' and FM 4470 Section 5.5 'Resistance to Foot Traffic'.	
Test Equivalency:	The test procedure in FM 4470 (1992) comply with test procedure prescribed in FM 4470 (2012).	
Code Compliance:	The product described herein has demonstrated compliance with FBC 2017 Section 1507.4	
Product Limitations:	Design wind loads shall be determined for each project in accordance with FBC 2017 Section 1609 or ASCE 7-10 using allowable stress design. The maximum support spacing listed herein shall not be exceeded. The design pressure for support spacing may be computed using rational analysis prepared by a Florida Professional Engineer or based on Union load span table. This evaluation report is not applicable in High Velocity Hurricane Zone. Fire classification is not within scope of this Evaluation Report. Refer to FBC 2017 Section 1505 and current approved roofing materials directory or ASTM	

FL 9555.6-R4 C2172-6 8.20.2017 Page 3 of 3

E108/UL790 report from an accredited laboratory for fire ratings of this product.

Supporting Documents: ASTM E1592 Test Reports ENCON Technology Inc. Project No. C2054-1, Reporting Date 10/16/15

> FM 4470 Test Report ENCON Technology Inc. C1583-1, Reporting Date 7/24/08

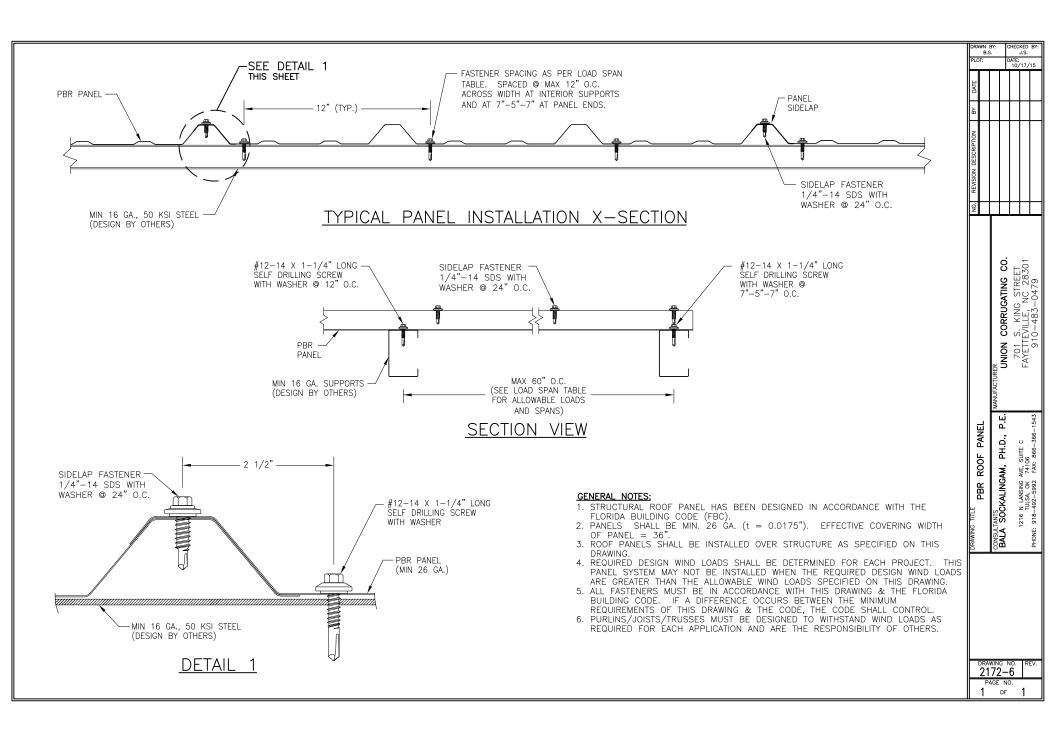

UNION CORRUGATING COMPANY PBR Roof Panel Allowable Design Loads

Support Spacing	Allowable Design Loads (psf)	
(in)	Gravity	Uplift
20	96.0	-163.0
22	87.3	-148.2
24	80.0	-135.8
27	71.1	-120.7
30	64.0	-108.7
33	58.2	-98.8
36	53.3	-90.6
39	49.2	-83.6
42	45.7	-77.6
45	42.7	-72.4
48	40.0	-67.9
51	37.6	-63.0
54	35.6	-56.2
57	33.7	-50.4
60	32.0	-45.5

Notes:

1. Allowable load is the lowest value of panel strength, connection strength & deflection limit of L/180.

- 2. Allowable load is applicable to three or more spans conditions.
- 3. Panels must be installed as per Evaluation Report FL 9555.6 and Union current installation procedure.
- 4. The structural capacity of support beam are not considered and must be examined independently.
- 5. Minimum support thickness is 16 ga.



1216 N Lansing Ave., Suite C Tulsa, Ok 74106 918 492 5992 Bala Sockalingam, Ph.D., P.E. FL 62240